

EFFECTS OF USED ENGINE OIL ON PRODUCTION OF HIGH-STRENGTH CONCRETE

Abstract

This research addressed the dual challenge of sustainable waste management through the reuse of used engine oil and the continuous demand for innovative high-strength concrete (HSC) production methods. The aim of this study was to investigate the effects of used engine oil on production of high-strength concrete. A detailed set of experiments was conducted involving the production and testing of full-scale reinforced concrete beams. The beams were cast using concrete mixes with a controlled dosage of superplasticizer, and their performance was compared with that of test mixes produced using varying dosages of used engine oil. The tests included fresh concrete properties such as slump and air content, as well as hardened properties including compressive, flexural, and splitting tensile strengths. The data obtained from the experimental tests underwent comprehensive analysis. This included plotting load–deflection curves and assessing the compressive strength, flexural strength, and tensile strength of both the control and test beams, cubes, and cylinders. Cracking patterns were also documented. At 56 days, the control mix achieved a compressive strength of 53.8 MPa, while mixes containing 0.15% and 0.30% used engine oil recorded 39.2 MPa and 25.7 MPa, representing reductions of 27.14% and 60.1%, respectively. The slump values increased from 210 mm (control) to 230 mm and 240 mm, showing a 9.52% –14.29% improvement in workability. The flexural strength load decreased from 57.08 kN (control) to 52.65 kN and 43.11 kN, indicating reductions of 7.76% and 24.47%, respectively. Similarly, splitting tensile strength loads changed from 96.48 kN (control) to 105.29 kN and 92.72 kN, showing a slight increase at 0.15% but a minor drop at 0.30%. The findings indicate that the incorporation of used engine oil enhances the workability of high-strength concrete but leads to a significant reduction in compressive and flexural strengths as the dosage increases. A low dosage of 0.15% used engine oil provided a limited improvement in workability and splitting tensile performance, though with a noticeable compromise in compressive strength, while a 0.30% dosage proved detrimental to overall mechanical performance. Consequently, used engine oil is not suitable as an admixture for high-strength structural concrete where strength is critical, but may be cautiously considered at very low dosages for non-structural applications where improved workability and sustainability benefits are prioritized.

Keywords

Used engine oil, High-strength concrete, Sustainable waste management, Reinforced concrete beams, Mechanical properties, Workability, Compressive strength, Flexural strength, Splitting tensile strength

1. Introduction

The construction industry increasingly relies on high-strength concrete (HSC) due to its superior mechanical performance and durability, particularly for infrastructure requiring high load-bearing capacity and long service life. However, sustainability concerns have driven research toward incorporating waste materials into concrete to reduce environmental impact (Aitcin, 2003). Used engine oil (UEO) is a significant environmental pollutant that poses risks to soil, water, ecosystems, and human health if improperly disposed of. Prior studies indicate that while small quantities of UEO may enhance concrete workability, they can adversely affect compressive strength after hardening (Oyekan and Kamiyo, 2011).

Despite growing interest in alternative materials, limited attention has been given to the behaviour of UEO in high-strength concrete systems, which differ markedly from conventional concrete due to their use of mineral admixtures and chemical superplasticizers. The introduction of UEO into such highly engineered mixtures may influence hydration, bonding, microstructure, and durability in ways not yet fully understood (Mehta and Monteiro, 2014). Improper disposal of waste oil further exacerbates environmental degradation, particularly in aquatic environments where toxic hydrocarbons and heavy metals threaten ecosystems and public health (Okoh et al., 2001). Although reprocessing and controlled destruction methods exist, the use of UEO as an admixture in concrete has been proposed as a potential waste-management strategy, though experimental validation remains insufficient (El-Fadel and Khoury, 2001).

2. Materials and methods

2.1 Materials

This study employed an experimental research design to evaluate the influence of used engine oil (UEO) on the fresh and hardened properties of high-strength concrete under controlled laboratory conditions. Concrete mixes incorporating UEO at dosages of 0.15% and 0.30% by weight of cement were prepared and compared with a control mix containing only a superplasticizer. The materials used included cement, natural sand, crushed coarse aggregates, potable water, steel reinforcement, used engine oil, and a commercial superplasticizer (CHRYSO). Standard laboratory equipment such as cube and cylinder moulds, a compression testing machine, dial gauges, and full-scale reinforced concrete beam moulds were employed to assess workability and mechanical performance. Eighteen reinforced concrete beams with uniform dimensions of $100 \times 100 \times 400$ mm were cast, reinforced with high-yield steel bars and stirrups, cured, and tested for flexural behaviour at 28 and 56 days. The UEO was sourced from a local automobile workshop, filtered before use, and introduced alongside a constant superplasticizer dosage of 0.88% by weight of cement, ensuring that observed performance variations could be attributed solely to the presence and dosage of used engine oil.

2.2 Mix Design

Concrete mixes were designed to achieve a target characteristic compressive strength of 50 MPa at 56 days using the DOE method. A water–cement ratio of 0.47, Portland cement Class 42.5, and a maximum aggregate size of 20 mm were adopted. The target mean strength was determined using a standard deviation of 8 MPa and a defective rate of 2.5% ($k = 1.96$). Free water content was fixed at 225 kg/m^3 , resulting in a cement content of approximately 478.7 kg/m^3 . Crushed coarse aggregate and uncrushed fine aggregate were used, with total aggregate content of about 1675 kg/m^3 , proportioned as 40% fine aggregate and 60% coarse aggregate. A commercial superplasticizer (CHRYSO) was added at a constant dosage of 0.88% by weight of cement. Used engine oil (UEO) was incorporated at 0% (control), 0.15%, and 0.30% by weight of cement, while all other mix parameters were kept constant to isolate its effect. Concrete specimens comprised $150 \times 150 \times 150$ mm cubes, $100 \times 100 \times 450$ mm reinforced beams, and cylinders, cast and tested at curing ages of 7, 14, 28, and 56 days. Compressive strength tests were conducted on cubes and cylinders, while flexural strength tests were performed on beams at 28 and 56 days.

Table 1(a): Mix Proportions per Cubic Metre (kg/m^3)

Mix ID	W/C	Cement	Fine Aggregate	Coarse Aggregate	Superplasticizer	UEO
Control	0.47	478.72	670.51	1005.77	4.21	0
0.15% UEO	0.47	478.72	670.51	1005.77	4.21	0.718
0.30% UEO	0.47	478.72	670.51	1005.77	4.21	1.436

Table 1(b): Batch Quantities per Specimen (kg)

Specimen Type	Mix ID	Water	Cement	Fine Aggregate	Coarse Aggregate	UEO
Cube ($150 \times 150 \times 150$ mm)	Control	0.759	1.616	2.263	3.395	0
	0.15%	0.759	1.616	2.263	3.395	0.0024
	0.30%	0.759	1.616	2.263	3.395	0.0048
Beam ($100 \times 100 \times 450$ mm)	Control	1.013	2.154	3.016	4.523	0
	0.15%	1.013	2.154	3.016	4.523	0.0032
	0.30%	1.013	2.154	3.016	4.523	0.0065
Cylinder	Control	0.353	0.752	1.052	1.578	0
	0.15%	0.353	0.752	1.052	1.578	0.0011
	0.30%	0.353	0.752	1.052	1.578	0.0011

2.3 Batching, Mixing, and Casting

Concrete constituents were batched by weight and mixed mechanically to ensure accuracy and uniformity, beginning with dry mixing of cement and aggregates followed by the controlled addition of water and admixtures to achieve a homogeneous mix. Fresh concrete was cast into lubricated steel moulds in layers, compacted by tamping, surface-finished, and left for 24 hours before demoulding and water curing at ambient temperature for 7, 14, 28, and 56 days in accordance with BS 1881: Part 125. A high-range water-reducing superplasticizer (CHRYSO® ZA 1538-01) was used at a constant dosage of 0.88% by weight of cement to enhance workability without compromising durability. Flexural test results were normalized using the compressive strength of companion cubes at corresponding ages to minimize variability and enable direct comparison between control and used engine oil (UEO) mixes, with normalized flexural strength expressed as the ratio of beam flexural strength to cube compressive strength. The used engine oil was sourced from an automobile workshop, filtered before use, securely stored during experimentation, and disposed of after testing in line with safe laboratory and environmental handling practices. See figure 1 below



Figure 1: Casting of cubes, cylinders and beams

2.4 Tests on Fresh and Hardened Concrete

The workability of fresh concrete was assessed using the slump test in accordance with BS EN 12350-2 (2009). For each mix (control, 0.15% UEO, and 0.30% UEO), freshly mixed concrete was placed in a standard slump cone in three equal layers, with each layer compacted using 25 strokes of a rounded tamping rod to remove air pockets. After levelling the top surface, the cone was lifted vertically, allowing the concrete to settle under its own weight. The difference in height between the mould and the settled concrete, called the slump value, indicated the mix's workability. The setting time of the cement–UEO paste was determined using the Vicat apparatus following ASTM C191 (2013). Pastes of standard consistency were placed in the Vicat mould, and the penetration of the needle was checked at intervals. The initial setting time was recorded when the paste began losing plasticity, while the final setting time was noted when the paste became completely rigid. For hardened concrete, flexural strength was measured on beams of 100 mm × 100 mm × 400 mm using a Compression Testing Machine. Each specimen was loaded at a uniform rate until failure, and the maximum load was recorded at 28 and 56 days. The flexural strength, σ , was calculated using the formula:

$$\sigma = \frac{FL}{wd^2} \text{ N/mm}^2$$

where F is the maximum applied load, L is the length of the beam, w is the width, and d is the depth. This test evaluated the beam's resistance to bending.

Split tensile strength was determined using cylindrical specimens of 100 mm diameter and 200 mm height. Specimens were placed horizontally in a Compression Testing Machine, and load was applied until splitting along the vertical axis occurred. The maximum load at failure was recorded, and the split tensile strength, f_t , was calculated as:

$$f_t = \frac{2P}{\pi DL} \text{ N/mm}^2$$

where P is the load at failure, D is the cylinder diameter, and L is its length. This method provides an indirect measure of the concrete's tensile capacity.

Compressive strength was measured on 150 mm × 150 mm × 150 mm concrete cubes using a Compression Testing Machine. The load was gradually applied until failure, and the compressive strength, f_c , was calculated as:

$$f_c = P/A \text{ (N/mm}^2\text{)}$$

where P is the ultimate load at failure and A is the cross-sectional area of the cube. This test determines the concrete's resistance to axial compression.

3. Results and Discussions

Sieve analysis determined the particle size distribution of the fine aggregate. The coefficients of uniformity and curvature were:

$$C_u = \frac{D_{60}}{D_{10}} = 4.898,$$

$$C_c = \frac{(D_{30})^2}{D_{10}D_{60}} = 0.566$$

indicating a well-graded sand.

Bulk density was calculated from the sample mass and cylinder volume:

$$\text{Mass} = 904.2 - 120.2 = 784 \text{ g,}$$

$$V = \pi r^2 h = \frac{22}{7} \times 4.42^2 \times 10.8 = 656.87 \text{ cm}^3,$$

$$\text{Bulk Density} = \frac{784}{656.87} = 1.19 \text{ g/cm}^3$$

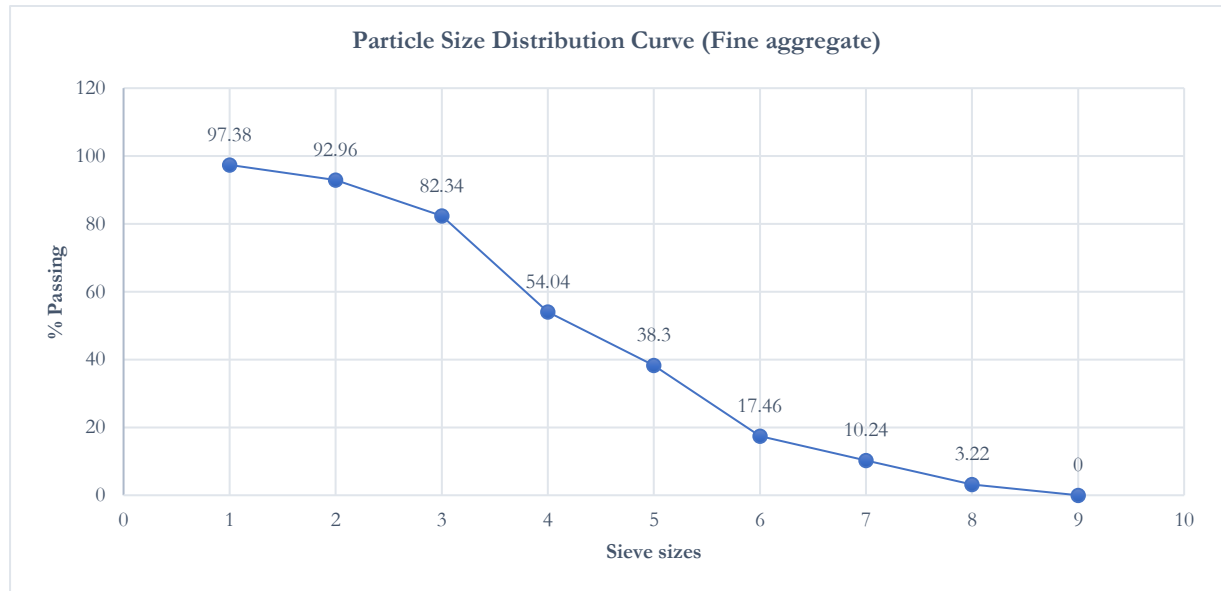


Figure 2: Particle Size Distribution Curve (Fine Aggregate)

Fine Aggregate: Specific gravity using the pycnometer method:

$$G_s = \frac{M_2 - M_1}{(M_2 - M_1) - (M_3 - M_4)} = 2.7$$

Coarse Aggregate: Particle size distribution was determined via sieve analysis. Water absorption and specific gravity were:

$$\text{Absorption} = \frac{\text{SSD} - \text{Dry}}{\text{Dry}} \times 100 = 0.346\%$$

$$G_s = \frac{\text{SSD}}{\text{SSD} - \text{Submerged}} = 2.65$$

Bulk density was calculated from container dimensions and mass:

$$V = \frac{\pi d^2}{4} \times h = 1.7851 \times 10^{-3} \text{ m}^3,$$

$$\text{Bulk Density} = \frac{2.7374}{1.7851 \times 10^{-3}} = 1533.46 \text{ kg/m}^3$$

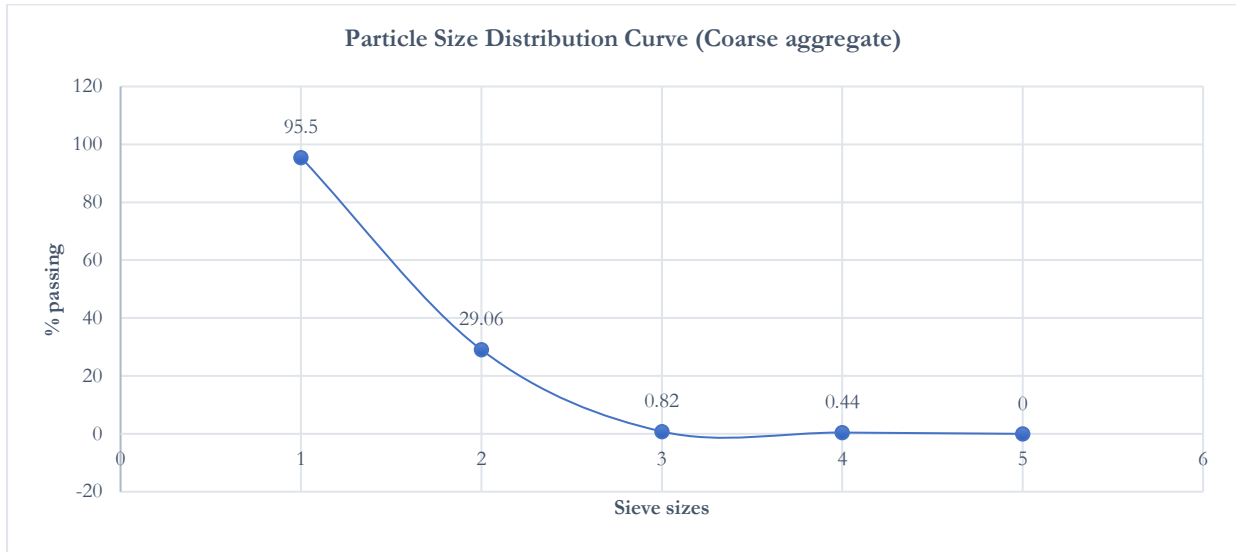


Figure 3: Particle Size Distribution Curve (Coarse Aggregate)

The aggregates exhibited strong mechanical performance, suitable for high-strength concrete. The Aggregate Crushing Value (ACV) and Aggregate Impact Value (AIV) were calculated as:

$$\text{ACV} = \frac{A - B}{A} \times 100 = \frac{2737.4 - 2251.2}{2737.4} \times 100 = 17.76\%$$

$$\text{AIV} = \frac{A - B}{A} \times 100 = \frac{363.5 - 336.5}{363.5} \times 100 = 7.43\%$$

Characterization of materials confirmed their suitability, with specific gravities of 2.70 (fine aggregate) and 2.65 (coarse aggregate), and low water absorption (0.346%), indicating dense, non-porous aggregates conducive to strength development.

Workability increased with UEO content, as shown by slump values: 210 mm (control), 230 mm (0.15% UEO), and 240 mm (0.30% UEO), reflecting the lubricating effect of UEO. Fresh concrete densities were 2502, 2481, and 2593 kg/m³ for control, 0.15%, and 0.30% UEO mixes, respectively, influenced by micro-air voids and oil's lower density (~0.85 g/cm³).

Hardened concrete compressive strength was determined by:

$$f_c = \frac{P}{A}, A = 150 \times 150 = 22,500 \text{ mm}^2$$

The control mix achieved 29.0, 35.2, 43.5, and 49.6 MPa at 7, 14, 28, and 56 days. Increasing UEO reduced strength consistently, with the 0.30% UEO mix showing a 48.2% reduction at 56 days. These results highlight that UEO improves workability but compromises long-term strength.

Statistical Analysis of Compressive Strength

The effects of UEO dosage and curing age on compressive strength were quantified using a multiple linear regression model:

$$\text{Compressive Strength} = \beta_0 + \beta_1(\text{UEO}) + \beta_2(\text{Day}) + \beta_3(\text{UEO} \times \text{Day})$$

The model showed strong predictive performance with $R^2 = 0.9285$, adjusted $R^2 = 0.9017$, residual standard error = 3.24 MPa, and F-statistic = 34.62 ($p < 0.001$), indicating that over 92% of the variance in compressive strength is explained by UEO content, curing age, and their interaction.

Interpretation of the coefficients reveals:

Intercept ($\beta_0 = 28.18$ MPa): Theoretical baseline compressive strength at Day 0 with 0% UEO.

UEO effect ($\beta_1 = -37.65$ MPa/unit): Each 1% increase in UEO reduces compressive strength by ~ 37.65 MPa, confirming a significant detrimental effect ($p = 0.021$).

Day effect ($\beta_2 = +0.42$ MPa/day): Strength increases by ~ 0.42 MPa per day of curing ($p < 0.001$), reflecting ongoing cement hydration.

Interaction effect ($\beta_3 = -0.92$ MPa/unit UEO-day): Negative interaction, borderline significant ($p = 0.054$), indicates that UEO's strength-reducing effect intensifies over longer curing periods.

These results quantitatively confirm that while curing time enhances strength, the presence of UEO significantly undermines compressive strength, with its effect compounded over time.

Interpolated Strength Surface and Mechanisms of Strength Reduction

A three-dimensional surface generated via Akima interpolation illustrated the combined effects of UEO content and curing age on compressive strength. The plot shows a descending gradient with increasing UEO, confirming systematic strength reduction, and an ascending ridge with curing age, reflecting ongoing hydration.

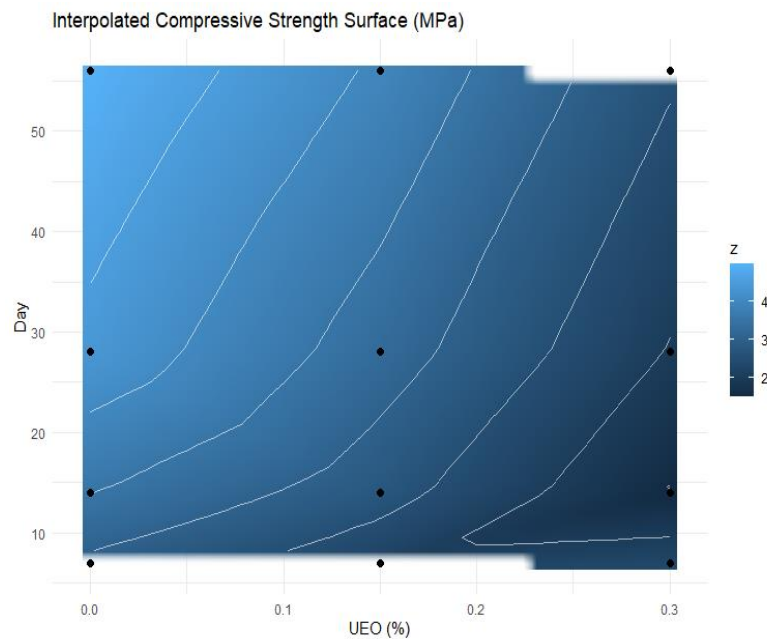


Figure 4: Akima interpolation of Strength Distribution

A pronounced depression at 0.30% UEO highlights the severe strength loss at higher oil dosages, particularly at later ages. The reduction in strength is attributed to several mechanisms: (i) Interfacial Transition Zone (ITZ) weakening, where UEO forms a hydrophobic film on aggregates, hindering cement-aggregate bonding; (ii) hydration interference, as the oil coating slows water access and retards cement reactions, consistent with longer setting times and the negative interaction effect; (iii) micro-void introduction, where trapped air reduces the solid load-bearing area; and (iv) reduced matrix density, as oil's lower density (~ 0.85 g/cm³) decreases the overall concrete compactness. Together, these factors explain the progressive compressive strength loss observed with increasing UEO content.

Flexural Strength Evaluation

Flexural strength of 100×100×400 mm beam specimens was tested at 28 and 56 days. At 28 days, the 0.15% UEO mix exhibited a notable increase in flexural strength (28.30 MPa, +57%) compared to the control (18.00 MPa), while the 0.30% UEO mix decreased to 13.95 MPa (-22%). By 56 days, all UEO-modified mixes showed lower flexural strengths than the control, with values of 13.40 MPa (0.15% UEO, -8%) and 11.00 MPa (0.30% UEO, -25%) relative to 14.60 MPa for the control.

The early-age improvement at 0.15% UEO is attributed to microstructural effects: limited internal lubrication promotes stress redistribution, controlled micro-void formation delays crack propagation, and increased matrix deformability enhances post-crack load-bearing capacity. These mechanisms improve ductility and bending resistance at low oil dosage. However, at higher dosages or later ages, UEO interferes with cement hydration and bond formation, weakening the interfacial transition zone and reducing flexural performance.

A regression model of the form:

$$\text{Flexural Strength} = \beta_0 + \beta_1(\text{UEO}) + \beta_2(\text{Day}) + \beta_3(\text{UEO} \times \text{Day})$$

showed poor statistical fit ($R^2 = 0.470$, adjusted $R^2 = -0.326$, $p = 0.678$), reflecting small sample size, high variability, and the non-linear response of flexural strength. Despite this, practical observations confirm the reproducible enhancement at 0.15% UEO, highlighting that low dosages can improve early-age flexural behavior even if longer-term effects are detrimental.

Split Tensile Strength Analysis

Cylindrical concrete specimens (100 mm × 200 mm) were tested at 28 and 56 days. At 28 days, the control mix recorded 2.933 MPa, while mixes with 0.15% and 0.30% UEO achieved 3.594 MPa (+22.5%) and 3.393 MPa (+15.7%), respectively. At 56 days, the control reached 3.071 MPa, with 0.15% UEO slightly higher at 3.351 MPa (+9.1%), whereas 0.30% UEO showed a marginal decrease to 2.951 MPa (-3.9%).

The initial improvement in split tensile strength with UEO is attributed to microstructural effects. Finely dispersed oil droplets act as compressible inclusions that bridge microcracks, absorb energy during crack propagation, and impart slight plasticity, reducing brittleness. Uniformly distributed micro-voids help redistribute tensile stresses, enhancing energy dissipation under the indirect tensile loading of the split test.

However, at 56 days, as the cement matrix densifies with continued hydration, the influence of UEO diminishes. The matured matrix strength dominates, and the interference of UEO with the interfacial transition zone (ITZ) increasingly offsets its crack-mitigating benefits, resulting in reduced tensile gains at later ages.

Comparative Analysis of Mechanical Properties

A comparative evaluation of compressive, flexural, and split tensile strengths at 28 and 56 days revealed distinct and evolving effects of UEO on concrete performance. At **28 days**, compressive strength was most severely affected, decreasing from 43.5 MPa (control) to 32.5 MPa (0.15% UEO) and 19.7 MPa (0.30% UEO). In contrast, flexural and tensile strengths exhibited a temporary enhancement at 0.15% UEO, with flexural strength rising from 18.0 to 28.3 MPa (+57%) and tensile strength from 2.93 to 3.59 MPa (+23%).

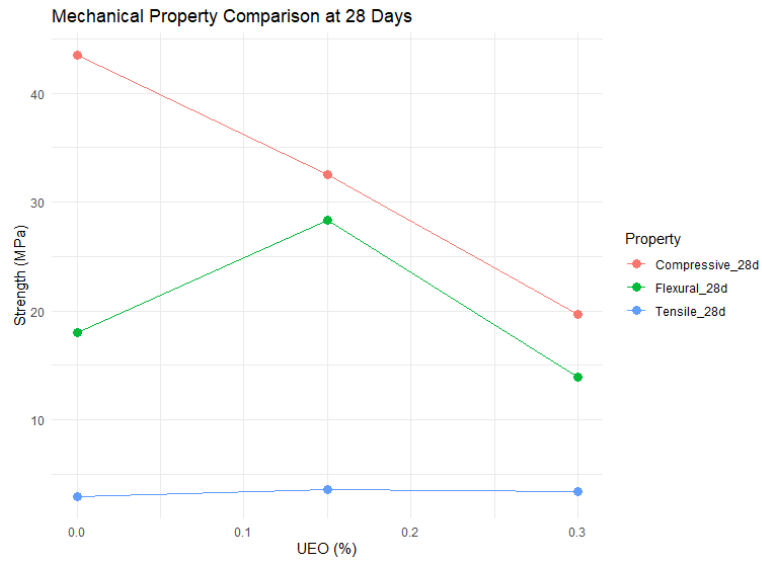


Figure 5: Mechanical Property Comparison at 28 days

This suggests a “sweet spot” at low UEO content where ductility benefits may outweigh compressive losses. At 0.30% UEO, all properties declined, indicating that this dosage exceeds the beneficial threshold.

By **56 days**, the trends evolved with concrete maturity. Compressive strength gains were observed for all mixes, but the relative deficit widened: 49.6 MPa (control), 39.2 MPa (0.15% UEO, -21%), and 25.7 MPa (0.30% UEO, -48%). Flexural strength advantages diminished; the 0.15% UEO mix dropped sharply from 28.3 to 13.4 MPa (-53%), reflecting the temporary nature of UEO’s microstructural benefits, likely due to ITZ degradation and continued matrix densification. In contrast, **split tensile strength remained enhanced** at 0.15% UEO (3.35 MPa, +9%) and nearly equivalent to control at 0.30% UEO (2.95 MPa), indicating sustained mechanisms that improve crack resistance and ductility even as compressive and flexural properties decline.

Property	Control	0.15% UEO	0.30% UEO
28d Compressive (MPa)	43.5 (100%)	32.5 (75%)	19.7 (45%)
28d Flexural (MPa)	18.0 (100%)	28.3 (157%)	14.0 (78%)
28d Split Tensile (MPa)	2.93 (100%)	3.59 (123%)	3.39 (116%)
56d Compressive (MPa)	49.6 (100%)	39.2 (79%)	25.7 (52%)
56d Flexural (MPa)	14.6 (100%)	13.4 (92%)	11.0 (75%)
56d Split Tensile (MPa)	3.07 (100%)	3.35 (109%)	2.95 (96%)

table 2- Comparative evaluation of compressive, flexural, and split tensile strengths at 28 and 56 days

Conclusion

This study investigated the effects of used engine oil (UEO) on high-strength concrete by incorporating 0%, 0.15%, and 0.30% UEO by weight of cement. Fresh properties, including slump, and hardened properties, compressive, flexural, and split tensile strengths, were evaluated over different curing periods.

The results indicate that UEO significantly enhances workability, with slump increasing from 210 mm (control) to 230 mm and 240 mm for 0.15% and 0.30% UEO, respectively. However, compressive strength declined with increasing UEO, decreasing from 53.8 MPa (control) to 39.2 MPa (0.15% UEO) and 25.7 MPa (0.30% UEO) at 56 days. Flexural strength and split tensile performance showed slight improvement at 0.15% UEO, suggesting a potential benefit for ductility and crack resistance, but both properties declined at 0.30% UEO.

Material characterization confirmed all aggregates and cement met high-strength concrete requirements, with fine aggregate specific gravity of 2.70 and well-graded sand ($C_u = 4.898$), and coarse aggregate demonstrating low water absorption (0.346%), ACV = 17.76%, and AIV = 7.43%.

A multiple linear regression model accurately predicted compressive strength:

$$\text{Compressive Strength} = 28.18 - 37.65(\text{UEO}) + 0.42(\text{Day}) - 0.92(\text{UEO} \times \text{Day})$$

The model ($R^2 = 0.9285$, residual standard error = 3.24 MPa) confirmed that UEO's negative effect on compressive strength intensifies with curing age. Predicted values closely matched experimental results (deviation <1.6%, MAE = 2.18 MPa, RMSE = 3.24 MPa, MAPE = 8.3%).

Recommendation

Based on the findings of this study, it is recommended that used engine oil (UEO) should not be incorporated into high-strength concrete for structural elements where compressive strength is critical, as reductions of 21–48% at 56 days render it unsuitable for load-bearing applications. If UEO is to be used, its dosage should be strictly limited to a maximum of 0.15% by weight of cement, since higher proportions lead to unacceptable strength losses. At this optimal dosage, UEO-modified concrete may be appropriate for non-structural applications, such as sidewalks, driveways, and partition walls, where moderate strength and improved workability are advantageous. Further research is encouraged to evaluate long-term durability properties, including creep, shrinkage, chloride penetration resistance, and freeze-thaw performance over extended periods of 365 days or more. Finally, any potential environmental benefits of recycling UEO must be carefully weighed against structural performance requirements before its adoption in concrete production.

References

- Abdelaziz, G. E. 2014. Utilization of used-engine oil in concrete as a chemical admixture. *Construction and Building Materials*, 63, 200–207.
- Ajao, O., Akintunde, O., & Olawale, S. (2024). Experimental Study of the Use of Demolition Wastes in the Production of High-Performance Concrete. *Global Journal of Research in Engineering & Computer Sciences*, 4(1), 11-30.
- Ahmad, J., Arbili, M. M., Alabduljabbar, H., and Deifalla, A. F. 2023. Concrete made with partially substituted corn cob ash: A review. *Case Studies in Construction Materials*, 19: e02345.
- Aitcin, P. C. 2003. *High-performance concrete*. Taylor and Francis.
- Al-Neshawy, F. 2010. *Recycling of waste engine oils in concrete: A sustainable approach*. In: *Proceedings of the International Conference on Sustainable Construction Materials and Technologies, Università Politecnica delle Marche, Italy*.

- Alsadey, S. 2018. *Effects of used engine oil as chemical admixture in concrete*. *International Journal of Scientific & Engineering Research*, 9(4), 117–122.
- Assaad, J. J. 2009. *Disposing used engine oils in concrete – Optimum dosage and compatibility with water reducers*. *Journal of Materials in Civil Engineering*, 21(9): 460–468.
- Aucelio, R., de Souza, V., de Campos, J., Miekeley, N. and Da Silva, L. 2007. *Chemical composition changes in used engine oil due to operation*. *Journal of Science, Technology, Mathematics and Education (JOSTMED)*.
- Ayoola, O. and Akaeze, C. 2012. Composition and contamination of spent engine oil and its environmental implications. *Journal of Biochemistry and Environmental Sciences*.
- Beddu, S., Shafiq, N., Nuruddin, M. F., Kamal, M., and Sadon, S. N. 2016. Effects of used engine oil as an admixture on concrete durability. *Current Journal of Applied Science and Technology*, 15(6): 1–10.
- Bilal S. H. and Ahmad A. R. 2002. Effect of used engine oil on structural behaviour of reinforced concrete elements. *Construction and Building Materials*, 16(7): 495–502.
- Bilal S.H. and Ahmad A. R. 2003. Effect of used engine oil on properties of fresh and hardened concrete. *Construction and Building Materials*, 17(5–6): 311–318.
- CIMAC, (2023). Used engine oil analysis: User interpretation guide. CIMAC Recommendation No. 30.
- Cvengros, J., Janosikova, D. and Kleinova, A. 2023. Study of polyaromatic hydrocarbons in current used motor oils. *Environmental Science and Pollution Research*. 30: 44521–44533.
- El-Fadel, M. and Khoury, R. 2001. Strategies for the management and recycling of used lubricating oils. *Journal of Environmental Management*, 62(1): 19–32.
- Etxeberria, M., Vázquez, E., Marí, A., and Barra, M. 2007. Influence of amount of recycled coarse aggregates and production process on properties of recycled aggregate concrete. *Cement and Concrete Research*, 37(5): 735–742.
- Farnam, Y., Monteiro, P. J. M., and Reinhardt, J. 2013. “Effect of Polycarboxylate Superplasticizers on the Rheology of Cement Pastes.” *Cement and Concrete Research*, 53: 93–100.
- Gambhir, M. L. 2004. *Concrete Technology: Theory and practice* (4th ed.). Tata McGraw-Hill Publishing Company Limited.
- Hussain, A. J., Imran, M. K., & Tayyeh, H. K. (2018). A comparison investigation on the effect of base oil and recycle oil on the concrete performance. *Journal of Engineering and Sustainable Development*, 22(2), 1–12.
- Hussen, S. S. 2016. Using of industrial waste as a green chemical admixture in concrete. *Kufa Journal of Engineering*, 7(1): 104–1.
- IJRIAS, 2023. Assessment of physicochemical quality, heavy metals, and total petroleum hydrocarbon concentration in surface water from communities of the Jones Creek oil field, Niger Delta, Nigeria. *International Journal of Research and Innovation in Applied Science*, 8(4): 56–65.
- Mehta, P. K., and Monteiro, P. J. 2014. *Concrete: Microstructure, properties, and materials*. 4th Edition. McGraw-Hill Education.
- Mi, R. B., Vongole, R., Nagraj, Y. and Naganna, S. R., 2023. Valorisation of incinerator bottom ash for the production of resource-efficient eco-friendly concrete: performance and toxicological characterization. *Materials Today: Proceedings*, 74: 410–419.
- Mindess, S., Young, J. F., & Darwin, D. 2003. *Concrete* (2nd edition). Prentice Hall, Upper Saddle River, New Jersey.
- Neville A.M. 1995. *Properties of concrete*. (4th edition). Prentice Hall.
- Neville, A. M. (2011). *Properties of Concrete* (5th edition). Pearson Education Limited.
- Neville, A. M., and Brooks, J. J. 2010. *Concrete Technology* (2nd edition). Pearson Education Limited.
- Okoh, A. I., Trejo-Hernandez, M. R. and Córdova-Rosa, S. M. 2001. Impact of petroleum hydrocarbons on aquatic ecosystems and human health. *Journal of Environmental Biology*, 22(3): 201–208.
- Oyekan, G. L. and Kamiyo, O. M. 2011. Effect of used engine oil on properties of concrete. *Nigerian Journal of Technology*, 30(3), 1–6.
- Puertas, F., Juárez, F. and Garcés, A. I. 2021. An evaluative review of recycled waste material utilization in high-performance concrete. *Civil Engineering Journal*, 7(4): 981–1002.
- Qian, C., Stroeven, P., and Ye, G. 2009. “Effect of Superplasticizers on the Microstructure and Durability of High-Performance Concrete.” *Construction and Building Materials*, 23(1): 330–337.

- Russell, H. G., and Burns, N. H. 1993. *Design and construction of high-strength concrete bridges*. Strategic Highway Research Program, National Research Council, Washington, D.C.
- Sakai, E. 1997. "Superplasticizers: Chemistry, Mechanisms, and Applications." *Concrete International*, 19(3): 45–50.
- Shafiq, N., Nuruddin, M. F. and Beddu, S. 2011. Properties of concrete containing used engine oil. *International Journal of Sustainable Construction Engineering and Technology*, 2(1), 72–82.
- Shafiq, N., Choo, C. S., & Isa, M. H. 2018. *Effects of used engine oil on slump, compressive strength and oxygen permeability of normal and blended cement concrete*. *Construction and Building Materials*, 25(10), 3853–3861.5
- Sharma, R., and Bansal, P. P. 2016. Use of different forms of waste plastic in concrete: A review. *Journal of Cleaner Production*, 112: 473–482.
- Shi, C., Wu, Y., and Riefler, C. 2014. *Characteristics and pozzolanic reactivity of ground glass in cement applications*. *Journal of Materials in Civil Engineering*, 26(2): 04014062.
- Siddique, R., and Khan, M. I. 2011. *Supplementary Cementing Materials*. Berlin: Springer.
- Taylor, H.F.W. 1997. *Cement Chemistry* (2nd Edition). London: Thomas Telford Publishing.
- Udonne, J. D. 2011. *A comparative study of recycling of used lubrication oils using distillation, acid and activated charcoal with clay methods*. *ARPJN Journal of Engineering and Applied Sciences*, 6(2): 82–92.